
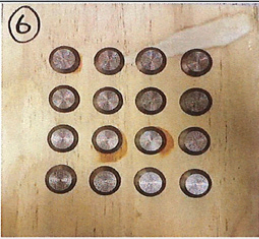


# Slip test results

## DBBRSSLNFN

Brass Tactile Bar

SLIP RESISTANCE TEST REPORT			
Project :	Slip Resistance Investigation		
Location of Test :	Auckland Laboratory		
Client :	CMT Group NZ Ltd - Total Tactilez		
Slider type :	FOUR-S, Prepared on P 400 (or equivalent) sand paper & Wet Lapping film.		
Specimen Description :	TacStud Alloy Bronze Studs with No Lip (Concentric circle design)		
Cleaning Procedure :	Wet Brush	Project Number : 1-LA410.00 Lab Ref. Number : AL2927/6 Client Ref. Number : -	
Test Type :	Unfixed		
Air Temp at Test (°C) :	19		
SLIP RESISTANCE TEST RESULTS			
Test № :	Test Direction :	Mean BPN :	Mean Coefficient of Friction* :
1	N/A	49	0.52
2		50	0.54
3		48	0.51
4		49	0.52
5		49	0.52
Average (SRV) :		49	0.52
Classification of pedestrian surface material in accordance with table 2, AS 4586:2013 :			<b>P4</b>
TEST METHOD			
Tests were carried out in accordance with Appendix A, AS 4586:2013, the classification is based on a test in the wet condition. <i>*Coefficient of friction obtained from: AS/NZS 3661.1 : 1993 Slip Resistance of Pedestrian Surfaces.</i>			
SAMPLE TESTED			
			
Tested By :	OPUS - G. Sandford <i>(Signature)</i>		
Designation :	Civil Engineering Technician		
Date Tested :	10/08/18		
<div style="display: flex; justify-content: space-between; font-size: small;"> <div>           LAF026 (08/17)            OPUS International Consultants Ltd.            Auckland Laboratory            Quality Management Systems Certified to ISO 9001         </div> <div>           7a Ride Way, Albany            Private Bag 101982, NS Mail Centre, North            Shore City 0745, New Zealand         </div> <div>           Page 1 of 1            Telephone +64 9 415 4660            Facsimile +64 9 415 4661            Website www.opus.co.nz         </div> </div>			